

## CELANEX® J600 | PBT | Mineral / Glass Reinforced

### Description


Celanex J-600 is a 40% glass/mineral reinforced resin providing excellent warpage resistance, surface gloss and good mechanical properties. Celanex J-600 is particularly suited to applications requiring flatness and good surface appearance in large parts, such as exterior automotive components.

| Physical properties                          | Value   | Unit                   | Test Standard     |
|--|---------|------------------------|-------------------|
| Density                                      | 1620    | kg/m <sup>3</sup>      | ISO 1183          |
| Melt volume rate (MVR)                       | 18      | cm <sup>3</sup> /10min | ISO 1133          |
| MVR test temperature                         | 265     | °C                     | ISO 1133          |
| MVR test load                                | 2.16    | kg                     | ISO 1133          |
| Mold shrinkage - parallel                    | 0.4-0.9 | %                      | ISO 294-4         |
| Mold shrinkage - normal                      | 0.6-1.2 | %                      | ISO 294-4         |
| Humidity absorption (23°C/50%RH)             | 0.2     | %                      | ISO 62            |
| Mechanical properties                        | Value   | Unit                   | Test Standard     |
| Tensile modulus (1mm/min)                    | 11000   | MPa                    | ISO 527-2/1A      |
| Tensile stress at break (5mm/min)            | 95      | MPa                    | ISO 527-2/1A      |
| Tensile strain at break (5mm/min)            | 2.1     | %                      | ISO 527-2/1A      |
| Flexural modulus (23°C)                      | 11000   | MPa                    | ISO 178           |
| Flexural strength (23°C)                     | 155     | MPa                    | ISO 178           |
| Charpy impact strength @ 23°C                | 38      | kJ/m <sup>2</sup>      | ISO 179/1eU       |
| Charpy impact strength @ -30°C               | 40      | kJ/m <sup>2</sup>      | ISO 179/1eU       |
| Charpy notched impact strength @ 23°C        | 6.5     | kJ/m <sup>2</sup>      | ISO 179/1eA       |
| Charpy notched impact strength @ -30°C       | 6.5     | kJ/m <sup>2</sup>      | ISO 179/1eA       |
| Unnotched impact str (Izod) @ 23°C           | 30      | kJ/m <sup>2</sup>      | ISO 180/1U        |
| Notched impact strength (Izod) @ 23°C        | 5.1     | kJ/m <sup>2</sup>      | ISO 180/1A        |
| Rockwell hardness                            | 69      | M-Scale                | ISO 2039-2        |
| Thermal properties                           | Value   | Unit                   | Test Standard     |
| Melting temperature (10°C/min)               | 225     | °C                     | ISO 11357-1,-2,-3 |
| DTUL @ 1.8 MPa                               | 190     | °C                     | ISO 75-1/-2       |
| DTUL @ 0.45 MPa                              | 220     | °C                     | ISO 75-1/-2       |
| DTUL @ 8.0 MPa                               | 80      | °C                     | ISO 75-1/-2       |
| Vicat softening temperature B50 (50°C/h 50N) | 205     | °C                     | ISO 306           |
| Coeff.of linear therm. expansion (parallel)  | 0.2     | E-4/°C                 | ISO 11359-2       |
| Coeff.of linear therm. expansion (normal)    | 0.68    | E-4/°C                 | ISO 11359-2       |
| Limiting oxygen index (LOI)                  | 22      | %                      | ISO 4589          |
| Flammability at thickness h                  | HB      | class                  | UL94              |
| thickness tested (h)                         | 0.82    | mm                     | UL94              |
| Electrical properties                        | Value   | Unit                   | Test Standard     |
| Relative permittivity - 100 Hz               | 5.1     | -                      | IEC 60250         |
| Relative permittivity - 1 MHz                | 4.4     | -                      | IEC 60250         |
| Dissipation factor - 100 Hz                  | 100     | E-4                    | IEC 60250         |
| Dissipation factor - 1 MHz                   | 220     | E-4                    | IEC 60250         |
| Volume resistivity                           | >1E13   | Ohm*m                  | IEC 60093         |
| Surface resistivity                          | >1E15   | Ohm                    | IEC 60093         |
| Electric strength                            | 35      | kV/mm                  | IEC 60243-1       |
| Comparative tracking index CTI               | 350     | -                      | IEC 60112         |

## CELANEX® J600 | PBT | Mineral / Glass Reinforced

| Test specimen production              | Value         | Unit | Test Standard |
|---------------------------------------|---------------|------|---------------|
| Processing conditions acc. ISO        | <b>7792-2</b> | -    | Internal      |
| Injection molding melt temperature    | <b>260</b>    | °C   | ISO 294       |
| Injection molding mold temperature    | <b>82</b>     | °C   | ISO 294       |
| Injection molding flow front velocity | <b>300</b>    | mm/s | ISO 294       |
| Injection molding hold pressure       | <b>48</b>     | MPa  | ISO 294       |

### Typical injection moulding processing conditions

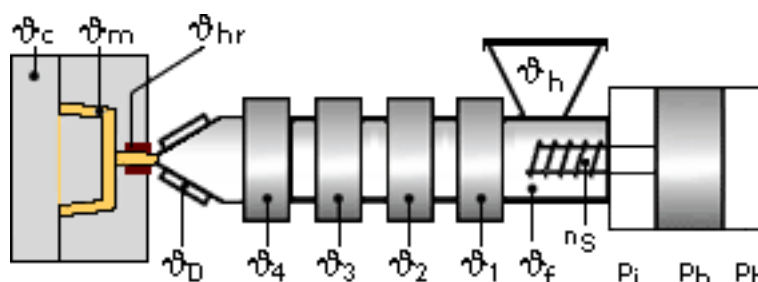

#### Pre Drying:

#### Necessary low maximum residual moisture content: 0.02%

To avoid hydrolytic degradation during processing, CELANEX resins have to be dried to a moisture level equal to or less than 0.02%. Drying should be done in a dehumidifying hopper dryer capable of dewpoints <-40°F (-40°C) at 250°F (121°C) for 4 hours.

For subsequent storage of the material in the dryer until processed (<= 60 h) it is necessary to lower the temperature to 100° C.

#### Drying time: 4 h

#### Drying temperature: 120 - 130 °C

#### Temperature:

|          | ϑ Manifold | ϑ Mold | ϑ Melt | ϑ Nozzle | ϑ Zone4 | ϑ Zone3 | ϑ Zone2 | ϑ Zone1 | ϑ Feed | ϑ Hopper |
|----------|------------|--------|--------|----------|---------|---------|---------|---------|--------|----------|
| min (°C) | 250        | 65     | 235    | 240      | 240     | 235     | 235     | 230     | 230    | 20       |
| max (°C) | 265        | 96     | 265    | 265      | 265     | 255     | 255     | 250     | 250    | 50       |

#### Speed:

#### Injection speed: medium-fast

### Contact Information

#### Americas

8040 Dixie Highway, Florence, KY 41042 USA

Product Information Service

t: +1-800-833-4882 t: +1-859-372-3244

Customer Service

t: +1-800-526-4960 t: +1-859-372-3214

e: [info-engineeredmaterials-am@celanese.com](mailto:info-engineeredmaterials-am@celanese.com)

#### Asia

4560 Jinke Road, Zhang Jiang Hi Tech Park

Shanghai 201203 PRC

Customer Service

t: +86 21 3861 9266 f: +86 21 3861 9599

---

**CELANEX® J600 | PBT | Mineral / Glass Reinforced**

---

e: info-engineeredmaterials-asia@celanese.com

**Europa**

Am Unisys-Park 1, 65843 Sulzbach, Germany

Product Information Service

t: +(00)-800-86427-531 t: +49-(0)-69-45009-1011

e: info-engineeredmaterials-eu@celanese.co

---

**General Disclaimer**

---

This publication was printed based on Celanese's present state of knowledge, and Celanese undertakes no obligation to update it. Because conditions of product use are outside Celanese's control, Celanese makes no warranties, express or implied, and assumes no liability in connection with any use of this information. Nothing herein is intended as a license to operate under or a recommendation to infringe any patents.

**NOTICE TO USERS:** Values shown are based on testing of laboratory test specimens and represent data that fall within the standard range of properties for natural material. These values alone do not represent a sufficient basis for any part design and are not intended for use in establishing maximum, minimum, or ranges of values for specification purposes. Colorants or other additives may cause significant variations in data values.

Properties of molded parts can be influenced by a wide variety of factors including, but not limited to, material selection, additives, part design, processing conditions and environmental exposure. Any determination of the suitability of a particular material and part design for any use contemplated by the users and the manner of such use is the sole responsibility of the users, who must assure themselves that the material as subsequently processed meets the needs of their particular product or use.

To the best of our knowledge, the information contained in this publication is accurate; however, we do not assume any liability whatsoever for the accuracy and completeness of such information. The information contained in this publication should not be construed as a promise or guarantee of specific properties of our products. It is the sole responsibility of the users to investigate whether any existing patents are infringed by the use of the materials mentioned in this publication.

Moreover, there is a need to reduce human exposure to many materials to the lowest practical limits in view of possible adverse effects. To the extent that any hazards may have been mentioned in this publication, we neither suggest nor guarantee that such hazards are the only ones that exist. We recommend that persons intending to rely on any recommendation or to use any equipment, processing technique or material mentioned in this publication should satisfy themselves that they can meet all applicable safety and health standards.

We strongly recommend that users seek and adhere to the manufacturer's current instructions for handling each material they use, and entrust the handling of such material to adequately trained personnel only. Please call the telephone numbers listed (+49 (0) 69 30516299 for Europe, +1 859-372-3244 for the Americas and +86 21 3861 9266 for Asia) for additional technical information. Visit our web site for the appropriate Safety Data Sheets (SDS) before attempting to process our products. Feel free to call Customer Services for additional assistance.

The products mentioned herein are not intended for use in medical or dental implants.

© 2014 Celanese or its affiliates. All rights reserved. (Published 25.November.2014)

Celanese®, registered C-ball design and all other trademarks identified herein with ®, TM, SM, unless otherwise noted, are trademarks of Celanese or its affiliates. Fortron is a registered trademark of Fortron Industries LLC.